

Product information

VESTALITE® P 311

(PRELIMINARY)

GENERAL DESCRIPTION

VESTALITE® P 311 is a polyurethane based resin formulation specially designed as matrix for fast curing prepreg applications. It gives room temperature stable, dry and non-tacky prepregs, which can be formed thermoplastically at 70 - 100°C and cured at temperatures between 150 and 180°C.

APPLICATION

Lower volume and automated production of structural FRP components like leaf springs (PCM - Technology). Specifically developed for Autoclave Technology.

BENEFITS

- Suitable for the production of thick parts – very low exothermy
- Excellent surface quality
- High toughness and ductility
- UV stable
- Storage stable and non-tacky at room temperature
- Automated preforming without binder
- Thermoplastic behavior for preforming


PRODUCT DATA

VESTALITE® P 311 Resin System	Value	Unit	Standard
Solids	60 - 65	%	Calculated
Color	0 - 1,5	Gardner	DIN EN ISO 4630
Viscosity at 23°C	200 - 4.000	mPa*s	ISO 3219, OECD 114
Exothermic Peak	166 - 168	°C	DSC [10K/min]
Geltime at 140°C	350 - 450	s	Geltimer (Plate)
Shelf Life at 23°C	8	week	
at -18°C	> 1	year	

RESIN PROPERTIES AFTER PREPREG STEP

VESTALITE® P 311 Resin System	Value	Unit	Standard
Tack	zero		
Volatiles	< 5	%	Weight Constancy
Exothermic Peak	158 - 160	°C	DSC [10K/min]
Shelf Life at 23°C	25	week	
at -18°C	>>1	year	
Curing Conditions at 140°C	20	min	
at 150°C	10		
at 160°C	5		
at 180°C	3		

VISCOSITY BUILD UP (5K/min)

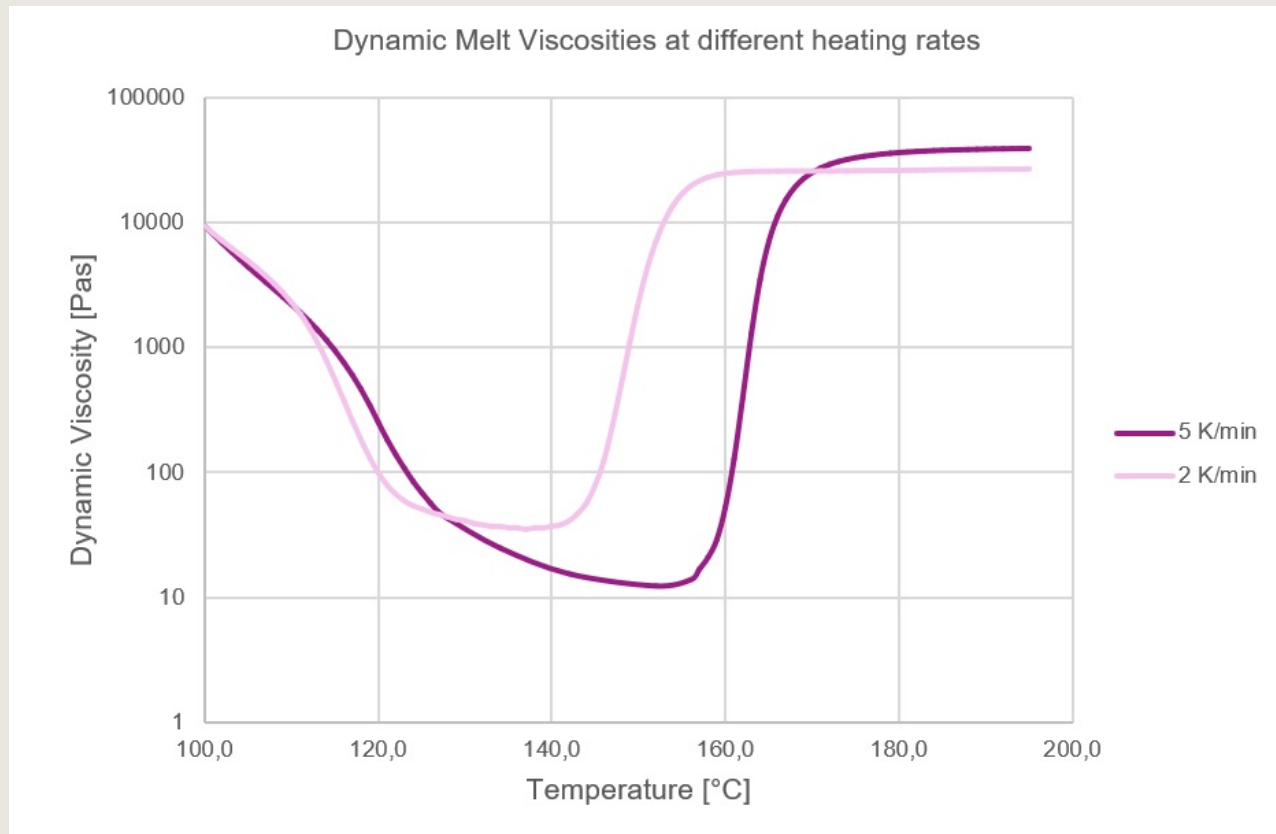

MATERIAL PROPERTIES

NEAT FORMULATION

Neat Resin properties		Value	Unit	Standard
Tensile Modulus	E_t	3400	MPa	DIN EN ISO 527-2
Tensile Stress at Break	σ_{tB}	85	MPa	DIN EN ISO 527-2
Tensile Strain at Break	ϵ_{tB}	2,3	%	DIN EN ISO 527-2
Poisson's ratio	ν	0,34	-	DIN EN ISO 527-1
Flexural Modulus	E_f	3300	MPa	DIN EN ISO 178
Flexural Strength	σ_{fB}	115	MPa	DIN EN ISO 178
Flexural Strain at Break	ϵ_{fB}	3,6	%	DIN EN ISO 178
Glass Transition Temperature (DSC)	T_g	140	°C	DIN EN ISO 11357-2
Fracture Toughness	K_{Ic}	1.7	MNm ^{-3/2}	ASTM D 5045-99
Chemical Shrinkage		0.9	%	pVT Method
CTE < T_g (20 - 130 °C)	α	60	ppm/k	TMA [1K/min]
> T_g (150 - 190°C)		195		
Density	ρ	1.13	g/cm ³	OECD 109

LAMINATE PROPERTIES

Glass Fiber Reinforced Laminates*		Value	Unit	Standard
Interlaminar Shear Strength (ILSS)	τ_M	80	MPa	DIN EN ISO 14130
Inerlaminar fracture toughness energy	G_{Ic}	2100	J/m ²	DIN EN 6033
Carbon Fiber Reinforced Laminates**				
Interlaminar Shear Strength (ILSS)	τ_M	90	MPa	DIN EN ISO 14130
Interlaminar fracture toughness energy	G_{Ic}	1500	J/m ²	DIN EN 6033

*Reinforcement: Glass Fiber-UD-NCF 591g/m²; Fiber Volume Content: 55 ± 2%

**Reinforcement: Carbon Fiber-UD-NCF 330 g/m²; Fiber Volume Content: 48 ± 2%



SAFETY AND HANDLING

For the most current Safety and Handling information, please refer to the Material Safety Data Sheet of VESTALITE® P 312 Resin.

Marl, March 4, 2019; This data sheet replaces all former issues.

VESTALITE® is a registered trademark of Evonik Industries AG or one of its subsidiaries.

Disclaimer

This information and all further technical advice are based on our present knowledge and experience. However, it implies no liability or other legal responsibility on our part, including with regard to existing third party intellectual property rights, especially patent rights. In particular, no warranty, whether express or implied, or guarantee of product properties in the legal sense is intended or implied. We reserve the right to make any changes according to technological progress or further developments. The customer is not released from the obligation to conduct careful inspection and testing of incoming goods. Performance of the product described herein should be verified by testing, which should be carried out only by qualified experts in the sole responsibility of a customer. Reference to trade names used by other companies is neither a recommendation, nor does it imply that similar products could not be used.

EVONIK RESOURCE EFFICIENCY GMBH

Business Line Crosslinkers
Paul-Baumann-Str. 1
45764 Marl
Germany

www.evonik.com/crosslinkers

For contact in your country, please visit: www.evonik.com/crosslinkers-contact

EVONIK CORPORATION

Business Line Crosslinkers
299 Jefferson Road,
Parsipanny, NJ 07054-0677
USA

EVONIK SPECIALITY CHEMICALS (SHANGHAI) CO., LTD.

Business Line Crosslinkers
55, Chundong Road
Xinzhuang Industry Park
Shanghai, 201108
China

